



International Scientific Organization
<http://iscientific.org/>
 Chemistry International
www.bosaljournals.com/chemint/



A historical perspective and the development of molecular imprinting polymer- A review

Nikesh B. Samarth^{1*}, Vinayak Kamble¹, Prakash A. Mahanwar¹, Ajay Vasudeo Rane², Abitha V. K³

¹Department Polymer and Surface Engineering, Institute of Chemical Technology, Nathalal Parekh Marg, Matunga, Mumbai, India, 400019.

²Centre for Green Technology, Institute of Chemical Technology, Nathalal Parekh Marg, Matunga, Mumbai, India, 400019.

³Department of Polymer Science and Rubber Technology, Cochin University of Science and Technology, Kerala, India, 682022

*Corresponding author's E. mail: n.b.samarth@gmail.com

ARTICLE INFO

Article type:

Review article

Article history:

Received June 2015

Accepted August 2015

October 2015 Issue

Keywords:

Molecular imprinting polymer

Solid-phase extraction

Analytical techniques

Cross-linked polymer

Historical perspective

ABSTRACT

Molecular imprinting is an emerging technology which enables us to synthesize the materials with highly specific receptor sites towards the target molecules. Molecularly imprinted polymers (MIPs) are a class of highly cross-linked polymer that can bind certain target compound with high specificity. Such techniques have been progressively employed in a wide scope of applications such as development of various analytical techniques such as solid-phase extraction (SPE), liquid chromatography, capillary electro chromatography, binding assays and biosensors, mostly in bio-analytical areas. The aim of this review paper is to give a fundamental description of the molecular imprinted polymer and to give the reader an insight into the main developments are discussed, Particular emphasis will be placed on their role as affinity materials in separation science. Discussing first general aspects in MIP history and preparation and then dealing with various application aspects.

© 2015 International Scientific Organization: All rights reserved.

Capsule Summary: A Molecularly Imprinted Polymer is a polymer that has been processed using the molecular imprinting technique which leaves cavities in polymer matrix with affinity to a chosen "template" molecule. The process usually involves initiating the polymerization of monomers in the presence of a template molecule that is extracted afterwards, thus leaving complementary cavities behind. Present paper details historical perspective and the development of molecular imprinting of polymer is reviewed in this article.

Cite This Article As: Nikesh B. Samarth, Vinayak Kamble, Prakash A. Mahanwar, Ajay Vasudeo Rane, Abitha V. K. 2015. A historical perspective and the development of molecular imprinting polymer-A review. Chemistry International 1(4) 202-210

INTRODUCTION

Molecular imprinting is an emerging technology which enables us to synthesize the materials with highly specific receptor sites towards the target molecules. Molecularly imprinted polymers (MIPs) are a class of highly cross-linked polymer that can bind certain target compound with high specificity. The polymers are prepared in the presence of the target molecule itself as the template. The concept behind the formation of the selective binding sites is schematically shown in Figure 1.

In brief, the template interacts with functional monomers before being cross-linked by cross-linker in polymerization process. The

specific binding site complementary to the target analyte is generated upon the removal of the template from the solid polymers (Lok et al., 2009). There have been several review articles on general introduction of MIP (Owens et al., 1999; Vasapollo et al., 2011; Wei et al., 2007). Here we review the history of molecular imprinting, from the introduction of the technique in conjunction with silica matrices in 1931 until the beginning of the 1970s, when the techniques was first applied to organic polymers. A brief overview is given regarding the evolution of molecular imprinting in organic polymers. However, although interest in the technique is new, the concept itself has a long history. 1972 marked the start of molecular imprinting technology as we know it today, when the laboratories of Wulff

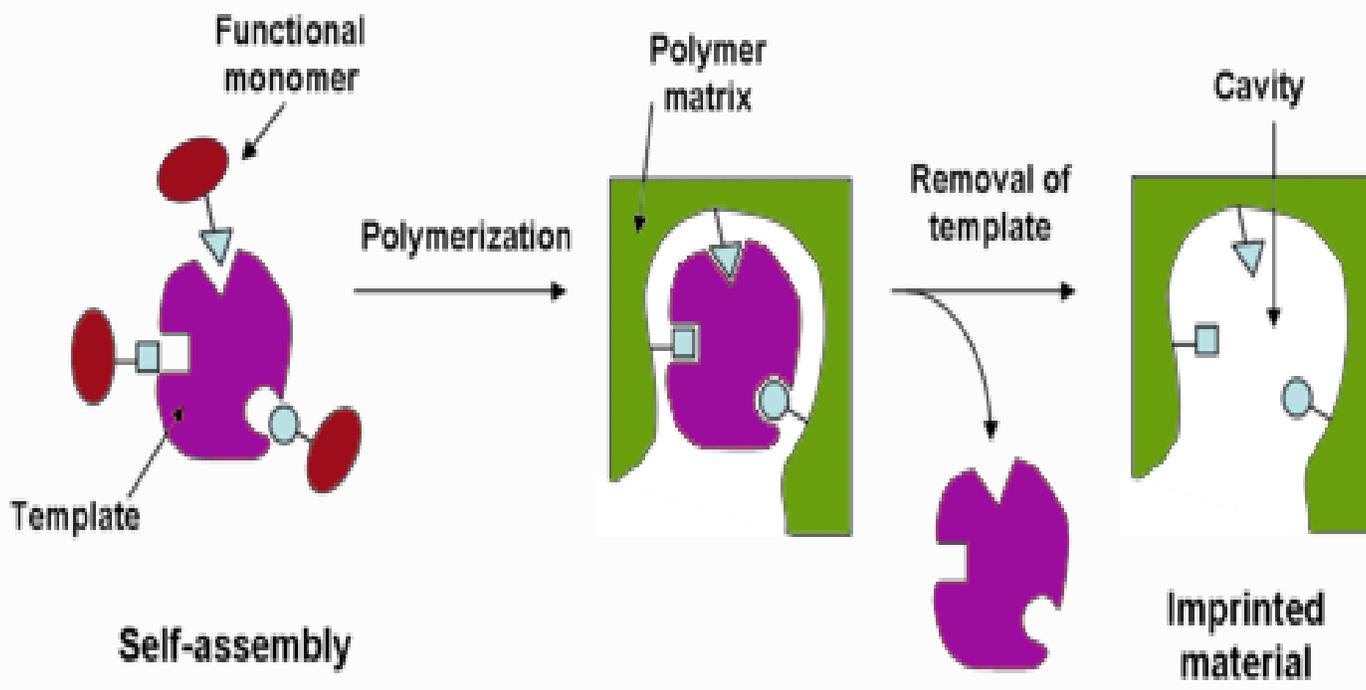


Fig. 1: Basic molecular Imprinting concept

and Klotz independently reported the preparation of organic polymer with predetermined ligand selectivities. Template molecules which were present during polymerization or derivatives therefore, were recognized by the resultant molecularly imprinted polymer (MIP). Wulff introduced a new approach that allowed the introduction of functional groups at defined positions in synthetic network polymers. This approach is often referred to as covalent molecular imprinting, to distinguish it from the noncovalent approach developed by Mosbach and his co-workers in the early 1980s. According to a recent comprehensive review (Vasapollo et al., 2011), the main advantages of MIPs are their high affinity and selectivity for the target molecule (template). MIPs have higher physical strength, robustness, resistance to elevated pressure and temperature and inertness against various chemicals (organic solvents, acids, bases, and metal ions) compared to biological media such as proteins and nucleic acids. Furthermore, their production costs are low and their lifetimes can be as long as several years at room temperature. MIP has excellent stability, ease of preparation and low cost for most of the target analysts make them attractive for numerous applications. Over 1450 references related to the use of MIPs in a large range of application areas have been recently collected (Alexander et al., 2006). Therefore, MIPs have been already successfully used as an alternative tool to these biological entities in several analytical fields such as separation of enantiomers in LC or CEC (Ansell, 2005; Zhao-Sheng Liu, 2007, binding assays (Ansell, 2004; Lavignac et al., 2004) and sensors (Avila et al., 2008; Holthoff and Bright, 2007). In recent years, the development of MIPs for solid-phase extraction (SPE) has been extensively reported (Blanco-Lopez et al., 2004; Caro et al., 2006; Fengxia et al., 2006; He et al., 2007; Pichon, 2007; Pichon et al., 2006; Tamayo et al., 2007) in the

areas of environmental, food and pharmaceutical analysis including their use as selective sorbents for the extraction or for the clean-up of different classes of compounds from various complex matrices. SPE is the most advanced application area of the MIP (Alexander et al., 2006). Most of the developments in MIP production during the last decade have come in the form of new polymerization techniques in an attempt to control the arrangement of monomers and therefore the polymers structure.

HISTORY- JOURNEY OF MIP FROM 1931 – 2013

In a paper published (Polyakov, 1931) by Polyakov reported the effects of presence of different solvents (benzene, toluene and xylene) on the silica pore structure during drying a newly prepared silica. When H_2SO_4 was used as the polymerization initiator (acidifying agent), a positive correlation was found between surface areas, e.g. load capacities, and the molecular weight of the respective solvents. Later on, in Dickey reported the polymerization of sodium silicate in the presence of four different dyes (namely methyl, ethyl, n-propyl and n-butyl orange). The dyes were subsequently removed, and in rebinding experiments it was found that silica prepared in the presence of any of these "pattern molecules" would bind the pattern molecule in preference to the other three dyes. Shortly after this work had appeared, several research groups pursued the preparation of specific adsorbents using Dickey's method. Some commercial interest was also shown by the fact that Merck patented a nicotine filter, consisting of nicotine imprinted silica, able to absorb 10.7% more nicotine than non-imprinted silica (Erlenmeyer, 1965). The material was intended for use in cigarettes, cigars and pipes filters. Shortly after this work had appeared, molecular imprinting attracted wide interest from the

scientific community as reflected in the 4000 original papers published in the field during for the period 1931–2009. The technology was then expanded by the effort of Mosbach and coworkers in 1980s (Andersson et al., 1984). The MIPs possess several advantages over the conventional immunosorbent (IS). They show high selectivity and affinity, high stability and the ease of preparation (Piletsky et al., 2006). The MIPs can be used repeatedly without loss of activity with high mechanical strength and durable to harsh chemical media, heat and pressure compared to biological receptors (Lavignac et al., 2004). Chemical stability studies demonstrated that the polymers kept >95% of their affinity even after 24 h of exposure to autoclaving treatment, triethylamine, 10M HCl acid and 25% NH₃. Heat treatment revealed that the polymers are thermally resilient and able to retain their chemical affinity, as the MIP will not degrade up to temperatures of 150 °C (Svenson and Nicholls, 2001). They can be stored for years without loss of affinity for the target analyte. Researches in this technology have grown rapidly due to its potential application in various fields, ranging from chemical, pharmaceutical, engineering, material science and biotechnological industries. Now a day's researcher focusing on, molecularly imprinted core-shell nanoparticles (Zhao et al., 2013) are the wonderful materials with the superiority of good accessibility to the target species and low mass-transfer resistance. As reported in a recent review (Lucena, 2012), MIPs have widely been utilized as the kernel coating materials for SBSE technique. Also in recent paper (Prasad et al., 2013) author reports a combination of molecularly imprinted stir bar sorptive extraction and complementary molecularly imprinted polymer-sensor for the analysis of dopamine as a biomarker of several neurodegenerative diseases occurred at ultra trace level.

REVIEW ON SYNTHESIS OF MOLECULARLY IMPRINTED POLYMERS

Molecular imprinting has been demonstrated in silica and in synthetic organic polymers, but it is organic polymers that have found the most favour and indeed probably have the most to offer to the affinity separation area. The rest of this article will therefore deal exclusively with molecular imprinting in the latter medium. Most methods for preparation of MIPS include three steps: firstly, mixing and interacting the functional monomers with the imprinted molecules; secondly, copolymerizing the cross-linkers with the functional monomers; thirdly, removing the template from the imprinted polymers. Recently, new methods for preparation of MIPS have been proposed, involving normal suspension polymerization (Hosoya, K.; Yoehizako, 1996), suspension polymerization in perfluorocarbon (Mayes et al., 1996), seed polymerization, graft polymerization, polymerization of reactive surfactants (Ye et al., 2001), precipitation polymerization (Ye et al., 1999), etc.

1. Choice of the template

The binding strength of the polymer as well as the fidelity in the recognition depends on the number and type of interaction sites, the template shape, and the monomer template rigidity (Sellergren, 1999). Templates offering multiple sites of

interactions for the functional monomer are likely to yield binding sites of higher specificity and affinity for the template. A MIP is usually synthesized for a specific analytical use that implies the choice of a given template molecule. The criteria to consider when selecting a candidate molecule are its cost, its availability and, of course, its chemical functionalities defining its ability to strongly interact with monomers. A quantitative structure binding relationship was demonstrated by imprinting a number of structurally related basic *N*-heterocyclic by copolymerization of methacrylic acid (MAA) and ethylene glycol dimethacrylate~(EDMA) (Shea et al., 1993; Vlatakis et al., 1993). High affinity and selectivity were reported when 9-ethyladenine was used as the template (Spivak et al., 1997; Yu and Mosbach, 1997). Sellergren and Dauwe observed similar effects in their studies on imprinting a series of similar structurally triazine templates. A notable increase in affinity and selectivity was obtained with an increase in the basicity of the templates. Furthermore, MIPs prepared with a template that forms a two-point interaction with MAA, such as ametryn exhibited higher affinity and selectivity for the template than for a structurally similar compound such as pronetryn (Dauwe and Sellergren, 1996). The shape and size of the template may in some cases be sufficient to create steric complementarity for efficient discrimination between two molecules. An example for the influence of template structure on the recognition properties of MIPs was observed in the imprinting of amino acids with *N*-protecting groups. Selectivity of amide MIPs was ascribed to the hydrogen bonds formed between the sample molecule and amide groups at the recognition sites of the MIP and to the size and shape of the amino acid molecule (Yu and Mosbach, 1997). Templates that possess conformational rigidity that can fit in the cavity of the polymer with minimal change in conformation will increase the affinity and selectivity in the recognition (Avila et al., 2008). In addition to the type of template, the ratio of the template to the functional monomer has been known to play a key role in the selectivity and sensitivity in the imprinted. Polymers when the possible interactions involved inside the matrix are taken into account. The optimum ratio has to be determined for each individual template. Investigations on the effect of stoichiometry have been reported in several imprinting studies. In 2008 Yi Ge et al. studied that successfully imprinting of large biomolecules such as proteins and cells (Yi Ge et al., 2008).

2. Types of Monomer and Cross-Linker

The choice of monomer is very important in order to create highly specific cavities designed for the template molecule. Typical functional monomers (Figure 2) are carboxylic acids (acrylic acid, methacrylic acid, vinyl benzoic acid), sulphonic acids (2 acrylamido-2-methylpropane sulphonic acid), heteroaromatic bases (vinylpyridine, vinylimidazole). The extensive use of methacrylic acid (MAA) is due to its capability to act both as hydrogen bond and proton donor and as hydrogen bond acceptor. Moreover, more strong functional monomers were developed via metal coordination interactions to bind specific amino acid sequences (Hart et al., 2001).

New functional monomers, based on polymerizable amidines and ureas, have been developed for stoichiometrically

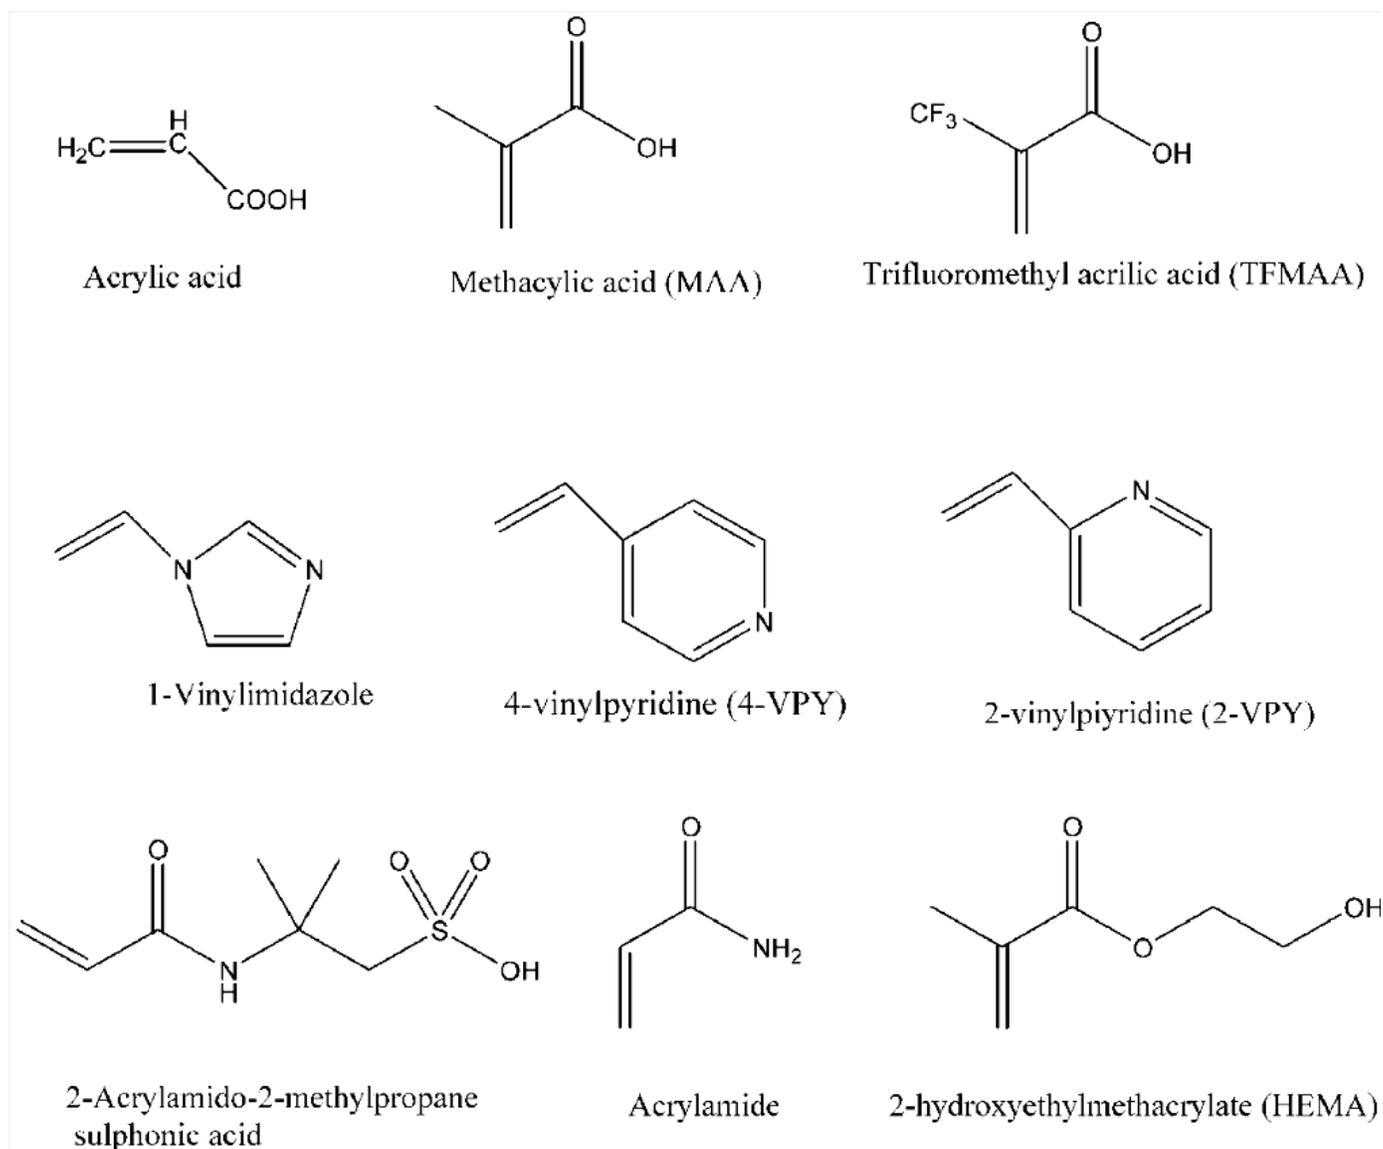


Fig. 2: Structure of the most common monomers used for molecular imprinting [42]

imprinted polymeric receptor of B-lactam antibiotics, reducing non-specific adsorption (Urraca et al., 2006). The best monomers for synthesizing imprinted materials are selected considering strength and nature of template-monomer interactions. The cross-linker also plays a major role in synthesis of imprinted polymer. The cross-linker is important in controlling the morphology of the polymer matrix, serves to stabilize the imprinted binding sites and imparts mechanical stability to the polymer matrix in order to retain its molecular recognition capability (Sellergren, 1999). Different cross-linkers have been used. Ethylene glycol dimethacrylate (EGDMA) and trimethylolpropane trimethacrylate (TRIM) are the most commonly employed. It has been found that the cross linker has less effect on the specific interactions between the template and functional monomers and more effect on the physical properties of the polymer reported by

some author. TRIM as cross-linker gives polymers with more rigidity, structure order and effective binding sites than EGDMA. Mosbach, (1998) reported that, In the case of precipitation polymerization method, by optimizing the amount of cross-linker and reducing the concentration of the template, the polymer binding properties are improved and the level of non-specific interactions is decreased (Ye et al., 2000). In another study, Mosbach, (1998) also reported that, the type of cross-linker strongly influences the final size and yield of MIP nanoparticles (Yoshimatsu et al., 2007). In fact, when divinylbenzene was used as the cross-linker, polydisperse MIP particles were obtained in low yield, whereas, trimethylolpropane trimethacrylate (TRIM) led to uniform nanoparticles in high yield (90%).

BRIEF REVIEW APPLICATION OF MIP

The different application areas, including separation sciences and purification, sensors and biosensors, catalysis and drug delivery are important application of MIPs because of its peculiar properties. It becomes an emerging technology with the potential for wide-ranging applications in food manufacturing, processing, analysis and quality control. It has been successfully applied in food microbiology, removal of undesirable components from food matrices, detection of hazardous residues or pollutants and sensors. Molecularly imprinted solid phase extraction (MISPE) is the most common application so far. Application of MIP in CEC is an area of increased attraction. Some author reported specific forms of MIPs such as monoliths particles and membranes etc. SPE is a very useful sample pretreatment/ enrichment method. The potential usefulness of MIP in drug delivery is very attractive, and there are some review articles on this topic (Alvarez-Lorenzo et al., 2004; Byrne et al., 2002; Cunliffe et al., 2005). Application of MIP as artificial enzymes or receptors for antibodies has also been reviewed in some articles. Application of MIP in sensors is a hot topic of a huge future commercial market. Among them, some author are focused on specified items such as electrochemical and optical sensors. In addition, there are some miscellaneous reviews of particular interests such as drug discovery with MIPs (Rathbone, 2005), MIPs incorporated with electrically conducting polymer (Pik et al., 2009), and template removal from the MIP matrix (Lorenzo et al., 2011).

1. Separation

MIPs were frequently used as Chiral Stationary Phases (MIP-CSPs) in High Performance Liquid Chromatography (HPLC) to obtain enantiomeric resolutions of racemic solutions of different compounds, such as amino acid derivatives and drugs. In 1985, the first studies were made by Mosbach group that realized an MIP sorbent used as stationary phase in LC, to separate amino acid derivatives (Selligren et al., 1985). Selligren and co-workers prepared an acrylic polymer by non-covalent imprinting procedure for selective enantioseparation of D or L-Phenylalanine ethyl esters to evaluate the enantio and substrate-selectivity for some amino acid derivatives (Szabelski et al., 2002). Solid Phase Extraction (SPE) is important area of application of MIPs in analytical chemistry. MIP for Solid-phase extraction (MISPE) has been applied both in on-line and off-line procedures. Molecular imprints were prepared using L-phenylalanine anilide as the print molecule and methacrylic acid as the functional monomer. Methacrylic acid interacts ionically with the primary amine of the print molecule and via hydrogen bonding with the amide function. In the HPLC mode such polymers were shown to exhibit efficient enantiomeric resolution of a racemic mixture of the original print molecule (Daniel et al., 1989). Researchers focused on the imprinting of amino acid derivatives was to attempt to make imprints of adducts of these compounds with pyridoxal to create sites which could recognize both the amino acid moiety and the pyridoxal moiety of the Schiff's base. It is reported that first imprinting carried out of a coenzyme-substrate analogue, N-pyridoxyl-L-phenylalaninanilide (I), allowing both enantiomeric separation

and facilitation of a model reaction involving pyridoxal (Andersson and Mosbach, 1989). In chromatographic applications, in early days optical resolution is achieved using as the stationary phase either a chiral material or chiral selectors coupled to a non-chiral support material. Now a day's molecular imprinting, has gained increasing interest for the preparation of chiral stationary phases. There are lots of work was performed on the chiral separation (Mayes and Mosbach, 1997; Mosbach et al., 1998; Wulff, 1995). By use of molecular imprinting, chirality may be introduced into polymer matrices starting from, in most cases, chiral building blocks. This chirality is thus a consequence of the asymmetry carried by the template. Molecularly imprinted materials have been employed as chiral matrices in different separation techniques (Armstrong et al., 1998; Fischer et al., 1991; Kriz et al., 1994; Schweitz et al., 1997). A characteristic of imprinted chiral stationary phases for chromatography is the predetermined elution order of the enantiomers, which depends only on the enantiomers used as the template molecule. For instance, if the D-enantiomers is used as the template, it will be retained more by the polymer than the L-enantiomers, and *vice versa*. The discrimination of enantiomers is often very efficient with molecularly imprinted materials yielding highly efficient chiral separations (Matsui et al., 1996; Ramstrom et al., 1994). Up to midst, the stationary phase most commonly used in thin-layer chromatography (TLC) has been silica particles. Much research has been directed toward the variation of the stationary phase in order to achieve selective interactions with the analyte. For instance, silica particles have been modified by introducing amino-, cyano-, or diol-bonded groups, thus changing the selectivity. An interesting approach would be to make use of the predetermined molecular recognition properties of MIPs. We therefore decided to investigate the use of MIPS as the stationary phase in TLC. This was expected to offer a quick and powerful analysis/separation technique which could be performed using simple and inexpensive equipment results successfully demonstrate the feasibility of the manufacture of thin-layer chromatography plates coated with molecularly imprinted polymers. TLC plates with specificity for a desired molecule (or enantiomers thereof) can be made for fast and simple analyses. In particular the predetermined chiral selectivity of the prepared TLC plates may be applicable in the pharmaceutical industry. The manufacture of optically pure drugs is of great importance in order to avoid possible side effects. The asymmetric synthesis of such drugs, or their large-scale enantiomeric separation on chiral stationary phases or molecularly imprinted polymers, could readily be followed by using molecularly imprinted thin-layer chromatography plates (Kriz et al., 1994). Scientists successfully prepared molecularly imprinted polymers (MIPS) for 4-nitrophenol by a thermal polymerization method using 4-vinylpyridine (4-VP) and ethylene glycol dimethacrylate (EDMA) as functional monomer and cross-linker, respectively. The obtained materials were evaluated with respect to their selective recognition properties for 4-nitrophenol by HPLC using organic and aqueous eluents. Furthermore, the specific binding sites that have been mated during the polymerization process were analyzed via radio ligand binding assays. The successful imprinting against 4-nitrophenol provides a new opportunity for advanced separation materials used in

environmental analysis (Janotta et al., 2001). Authors attempted to fabricate a highly selective and sensitive bulk acoustic wave (BAW) sensor based on molecularly imprinted microspheres (MIM). Dipyridamole, 2, 2', 2'', 2'''-(4-8-dipiperidinopyrimido [5,4-d] pyrimidine-2, 6-diylidinihilo tetra ethanol, was used as template. The MIPS were characterized by using TEM and the Scatchard analysis. Influencing factors such as ethanol, pH value and the weight ratio of polyvinyl chloride (PVC) to MIM were investigated. The sensors, which were modified by WC, were also successfully applied to the determination of Dipyridamole in water and urine, and the results were satisfactory (Zhang et al., 2003). Report that long open tubular molecular imprinted polymer capillary columns with excellent separation efficiencies in chiral and non-chiral separation by capillary electrochromatography. Authors reported that Molecularly Imprinted Chromatography is one of the most traditional applications of molecularly imprinted polymers especially for Liquid Chromatography (LC) with MIPS usually synthesized by bulk polymerization, ground and sieved mechanically and subsequently packed in a chromatographic column (Haginaka, 2008). For preparative applications, membranes can be used as the separation matrices, with the benefit that a continuous process can be designed, as compared to the batch wise operation of chromatography. There have been a few reports in the literature dealing with molecularly imprinted membranes that exhibit selective binding or transport of a target analyte (Hedborg et al., 1993; Mathew-Krotz and Shea, 1996; Kobayashi et al., 1995; Piletsky et al., 1995). Some of them were designed for application as the recognition element in sensors (Hedborg et al., 1993; Piletsky et al., 1995). Membranes were prepared either as free-standing thin films or thin polymer films on the surface of solid supports following standard imprinting recipes. Others have employed a phase-inversion precipitation technique starting from linear polymer precursors (Kobayashi et al., 1995). In a paper author reports a different approach towards the development of molecularly imprinted polymer membranes for the resolution of racemates. To obtain mechanically stable membranes for preparative application, the imprinted polymer was synthesized in the pores of polypropylene membranes. The amino acid derivative CBZ-tyrosine was chosen as the target molecule, and a standard polymer recipe for non-covalent imprinting was used (Dzgoev and Haupt, 1999). Lei Ye et al., reported preparation of extremely stable and specific adsorbents for the product Z-L-Asp-L-Phe-OMe (Z-aspartame) using the emerging technique of molecular imprinting. This new methodology may find use in various synthetic applications such as high pressure and temperature stability, allowing MIPS to withstand sterilization conditions

2. Sensor

MIPs exhibit exceptional chemical and thermal stability. These desirable properties have led to tremendous interest in the use of MIPS as recognition elements in chemical sensors and biosensors (Haupt and Mosbach, 2000). The general approach involves attaching the MIP onto the surface of a transducer that sensors binding events between the MIP and the target analyte and sends quantifiable signal to the user. In this paper, we attempted to

fabricate a highly selective and sensitive BAW sensor based on molecular imprinted microspheres (MIM). Dipyridamole, 2, 2', 2'', 2'''-(4-8-dipiperidinopyrimido [5, 4-d] 3 pyrimidine-2, 6-diylidinihilo tetra ethanol, was used as template. The MIPS were characterized by using TEM and the Scatchard analysis. Influencing factors such as ethanol, pH value and the weight ratio of polyvinyl chloride (PVC) to MIM were investigated. The sensors, which were modified by PVC, were also successfully applied to the determination of Dipyridamole in water and urine, and the results were satisfactory (Zhang et al., 2003).

3. Drug Discovery

Recent developments in the field of biomaterials are based on molecular design of polymers with improved surface and bulk properties. Novel techniques of surface modification by addition of tethered chains can lead to materials with the ability to recognize biological and pharmaceutical compounds. Authors examined that Acrylic-based hydrogels are well-suited for mucoadhesion due to their flexibility and nonabrasive characteristics which reduce damage-causing attrition to the tissues in contact. However, the adhesive and drug delivery capabilities of these devices can continue to be improved as presently known bioadhesive materials are modified and more bioadhesive materials are discovered. Tethering of long PEG chains on PAA hydrogels and their copolymers can be achieved by grafting reactions involving thionyl chloride, followed by PEG grafting. Also reported that various forms of adhesive hydrogels based on poly(acrylic acid) research. In our recent work, we have shown that (PAA) or poly (methacrylic acid) (PMAA) exhibit an unusual property of inhibition of the degradation of various peptides and proteins (including insulin) by proteolytic enzymes (Bures et al., 2001).

CONCLUSION

The preparation methods of MIP include embedding method, affinity imprinting, freeze drying and surface imprinted method. Research direction for MIP in future includes understanding the mechanism of molecular imprinting and identification from molecular level, exploring new synthetic method, realizing the transfer of mol. Imprinting technique from organic phase to water phase, from non-polar solvent environmental and extending its application field.

REFERENCES

- Alexander, C., Andersson, H.S., Andersson, L.I., Ansell, R.J., Kirsch, N., Nicholls, I.A., O'Mahony, J., Whitcombe, M.J., 19, 2006, Molecular imprinting science and technology: a survey of the literature for the years up to and including 2003. *Journal of Molecular Recognition* 19, 106 - 180.
- Alvarez-Lorenzo, C., Concheiro, A., 2004. Molecularly imprinted polymers for drug delivery. *Journal of Chromatography B* 804, 231–245.

- Andersson, L., Sellergren, B., Mosbach, K., 1984. Imprinting of amino acid derivatives in macroporous polymers. *Tetrahedron Letter* 25, 5211-5214.
- Andersson, L.I., Mosbach, K., 1989. Molecular imprinting of the coenzyme-substrate analogue N-pyridoxyl-L-phenylalaninamide, *Makromol. Chem. Rapid Communications* 10, 491-495.
- Ansell, D.J., 2005. Molecular imprinted polymers for separation science: A review of reviews. *Advanced Drug Delivery Reviews* 57, 1809-1835.
- Ansell, R.J., 2004. Molecularly imprinted polymers in pseudoimmuno assay. *Journal of Chromatography B* 804, 151 - 165.
- Armstrong, D.W., Schneiderheinze, J.M., Hwang, Y-S., Sellergren, B., 1998. Bubble fractionation of enantiomers from solution using molecularly imprinted polymers as collectors. *Analytical Chemistry* 70, 3717-3719.
- Avila, M., Zougagh, M., Rios, A., Escarpa, A., 2008. Molecularly imprinted polymers for selective piezoelectric sensing of small molecules. *Trends in Analytical Chemistry* 27, 54 - 65.
- Blanco-Lopez, M.C., Lobo-Castanon, M.J., Miranda-Ordieres, A.J., Tunon-Blanco, P., 2004. Electrochemical sensors based on molecularly imprinted polymers. *Trends in Analytical Chemistry* 23, 36-48.
- Bures, P., Huang, Y., Oral, E., Peppas, N.A., 2001. Surface modifications and molecular imprinting of polymers in Medical and pharmaceutical applications. *Journal of Controlled Release* 72, 25-33
- Byrne, M.E., Park, K., Peppas, N.A., 2002. Molecular imprinting within hydrogels. *Advanced Drug Delivery Reviews* 54, 149-161.
- Caro, E., Marce, R.M., Borrell, F., Cormack, P.A.G., Sherrington, D.C., 2006. Application of molecularly imprinted polymers to solid-phase extraction of compounds from environmental and biological samples. *Trends in Analytical Chemistry* 25, 143-154.
- Cunliffe, D., Kirby, A., Alexander, C., 2005. Molecularly imprinted drug delivery systems. *Advanced Drug Delivery Reviews* 57, 1836-1853.
- Dauwe, C., Sellergren, B., 1996. Influence of template basicity and hydrophobicity on the molecular recognition properties of molecularly imprinted polymers. *Journal of Chromatography A* 753(2), 191-200.
- Dzgoev, A., Haupt, K., 1999. Enantioselective Molecularly Imprinted Polymer Membranes. *Chirality* 11, 465-469.
- Fengxia, Q., Hanwen, S., Hongyuan, Y., Ho, R.K., 2006. Molecularly Imprinted Polymers for Solid Phase Extraction. *Chromatographia* 64, 625-634.
- Fischer, L., Muller, R., Ekberg, B., Mosbach, K., 1991. Direct enantioseparation of β -adrenergic blockers using a chiral stationary phase prepared by molecular imprinting. *Journal of the American Chemical Society* 113, 9358-9360.
- Ge, Y., Turner, A.P.F., 2008. Too large to fit? Recent developments in macromolecular imprinting, *Trends in Biotechnology* 26, 218-224
- Haginaka, J., 2008. Monodispersed, molecularly imprinted polymers as affinity-based chromatography media. *Journal of Chromatography B* 866, 3-13.
- Hans, E., 1965. Silica gel filter for removing nicotine from tobacco smoke, Patent DE 1965-M64131
- Hart, B.R., Shea, K.J., 2001. Synthetic peptide receptors: Molecularly imprinted polymers for the recognition of peptides using peptide-metal interactions. *Journal of the American Chemical Society* 123, 2072-2073.
- Haupt, K., Mosbach, K., 2000. Molecularly imprinted polymers and their use in biomimetic sensors. *Chemical Reviews* 100, 2495-504.
- He, C., Long, Y., Pan, J., Li, K., Liu, F., 2007. Application of molecularly imprinted polymers to solid-phase extraction of analytes from real samples. *Journal of Biochemical and Biophysical Methods* 70(2), 133-150.
- Hedborg, E., Winquist, F., Lundstrom, I., Andersson, L.I., Mosbach, K., 1993. Some studies of molecularly imprinted polymer membranes in combination with field-effect devices. *Sensors and Actuators A* 37-38, 796-799.
- Holthoff, E.L., Bright, F.V., 2007. Molecularly templated materials in chemical sensing. *Analytica Chimica Acta* 594, 147 - 161.
- Hosoya, K., Yoshizako, K., Shirasu, Y., Kimata, K., Araki, T., Tanaka, N., Haginaka, J., 1996. Molecularly imprinted uniform-size polymer-based stationary phase for high-performance liquid chromatography structural contribution of cross-linked polymer network on specific molecular recognition. *Journal of Chromatography A* 728(1-2), 139-147.
- Janotta, M., Weiss, R., Mizaikow, B., Bruggemann, O., Yeb, L., Mosbach, K., 2001. Molecularly imprinted polymers for Nitrophenols - an advanced separation Material for environmental analysis. *International Journal of Environmental Analytical Chemistry* 80(2), 75-86.
- Kobayashi, T., Wang, H.Y., Fujii, N., 1995. Molecular imprinting of theophylline in acrylonitrile-acrylic acid copolymer membrane. *Chemistry Letters* 10, 927-928.
- Kriz, D., Berggren-Kriz, C., Andersson, L.I., Mosbach, K., 1994. Thin-layer chromatography based on the molecular imprinting technique. *Analytical Chemistry* 1994 66, 2636-2639.
- Kriz, D., Kriz, C.B., Andersson, L.I., Mosbach, K., 1994. Thin-Layer Chromatography Based on the Molecular Imprinting Technique. *Analytical Chemistry* 66, 2636-2639.
- Lavignac, N., Allender, C.J., Brain, K.R., 2004. Current status of molecularly imprinted polymers as alternatives to antibodies in sorbent assays. *Analytica Chimica Acta* 510, 139-145.
- Lavignac, N., Allender, C.J., Brain, K.R., 2004. Current status of molecularly imprinted polymers as alternatives to antibodies in sorbent assays. *Analytica Chimica Acta* 510, 139-145.
- Lee, M., Shea, R.G., Hartley, J.A., Lown, J.W., Kissinger, K., Dabrowiak, J.C., Vesnaver, G., Breslauer, K.J., Pon, R.T., 1989. Molecular recognition between oligopeptides and nucleic acids. Sequence specific binding of (4S)-(+)- and (4R)-(-)-dihydrokikumycin B to DNA deduced from ^1H NMR, footprinting studies and thermodynamic data. *Journal of molecular recognition* 2, 6-17

- Lok, C.M., Son, R., 2009. Application of molecularly imprinted polymers in food sample analysis – a perspective, *International Food Research Journal* 16, 127-140.
- Lorenzo, R.A., Carro, A.M., Alvarez-Lorenzo, C., Concheiro, A., 2011. To Remove or Not to Remove? The Challenge of Extracting the Template to Make the Cavities Available in Molecularly Imprinted Polymers (MIPs). *International Journal of Molecular Sciences* 12, 4327–4347.
- Lucena, R., 2012, Extraction and stirring integrated techniques: examples and recent advances. *Analytical and Bioanalytical Chemistry* 403, 2213-2223.
- Maier, N.M., Lindner, W., 2007. Chiral recognition applications of molecularly imprinted polymers: a critical review. *Analytical and Bioanalytical Chemistry* 389, 377–397.
- Mathew-Krotz, J., Shea, K.J., 1996. Imprinted polymer membranes for the selective transport of targeted neutral molecules. *Journal of the American Chemical Society* 118, 8154–8155.
- Matsui, J., Nicholls, I.A., Takeuchi, T., 1996. Highly stereoselective molecularly imprinted polymer synthetic receptor for cinchona alkaloids. *Tetrahedron: Asymmetry* 2, 1357–1361.
- Mayer, A.G., Mosbach, K., 1997. Molecularly Imprinted Polymers: Useful Materials for Analytical Chemistry. *Trends in Analytical Chemistry* 16, 321–332.
- Mayer, A.G., Andersson, L.I., Mosbach, K., 1994. Sugar Binding Polymers Showing High Anomeric and Epimeric Discrimination Obtained by Noncovalent Molecular Imprinting. *Analytical Biochemistry* 222, 483-488.
- Mosbach, K., Haupt, K., Liu, X-C., Cormack, P.A.G., Ramstrom, O., 1998. Molecular Imprinting: Status Artis et Quo Vadere? In: Bartsch RA, Maeda M, editors. *Molecular and ionic recognition with imprinted polymers*. ACS Symposium Series 703. Washington DC: American Chemical Society, 29–48.
- Opik, A., Menaker, A., Reut, J., Syritski, V., 2009. Molecularly imprinted polymers: a new approach to the preparation of functional materials. *Proceedings of the Estonian Academy of Sciences* 58(1), 3–11.
- Owens, P. K., Karlsson, L., Lutz, E. S. M., Andersson, L. I., *Trends Anal. Chem.* 1999, Molecular imprinting for bio- and pharmaceutical analysis 18, 146–154.
- Pichon, V., 2007, Selective sample treatment using molecularly imprinted polymers. *Journal of Chromatography A* 1152, 41-53.
- Pichon, V., Chapuis-Hugon, F., 2008. Role of molecularly imprinted polymers for selective determination of environmental pollutants—A review. *Analytica Chimica Acta* 622(1–2), 48–61.
- Pichon, V., Haupt, K., 2006, Affinity Separations on Molecularly Imprinted Polymers with Special Emphasis on Solid-Phase Extraction. *Journal of Liquid Chromatography & Related Technologies* 29, 989-1023.
- Piletsky, S.A., Piletskaya, E.V., Elgersma, A.V., Yano, K., Karube, I., Parhometz, Y.P., 1995. Atrazine sensing by molecularly imprinted membranes. *Biosensors and Bioelectronics* 10, 959–964.
- Piletsky, S.A., Turner, N.W., Laitenberger, P., 2006. Molecularly imprinted polymers in clinical diagnostics future potential and existing problems. *Medical Engineering and Physics* 28, 971-977.
- Polyakov, M.V., 1931. Adsorption properties and structure of silica gel. *Zhurnal fizicheskoi khimii* 2S, 799–804
- Prasad, B.B., Srivastava, A., Tiwari, M.P., 2013. Highly selective and sensitive analysis of dopamine by molecularly imprinted stir bar sorptive extraction technique coupled with complementary molecularly imprinted polymer sensor, *Journal of Colloid and Interface Science* 396, 234–241.
- Ramstrom, O., Ansell, R., 1998. Molecular imprinting technology: Challenges and prospects for the future. *Chirality* 10, 195–209.
- Ramstrom, O., Nicholls, I.A., Mosbach, K., 1994. Synthetic peptide receptor mimics: Highly stereoselective recognition in non-covalent molecularly imprinted polymers. *Tetrahedron: Asymmetry* 5, 649–656.
- Rathbone, D. L., 2005. Molecularly imprinted polymers in the drug discovery process. *Advanced Drug Delivery Reviews* 57, 1854–1874.
- Schweitz, L., Andersson, L.I., Nilsson, S., 1997. Capillary electrochromatography with molecular imprint-based selectivity for enantiomer separation of local anaesthetics. *Journal of Chromatography A* 792, 401–409.
- Sellergren, B., 1999. Polymer- and template-related factors influencing the efficiency in molecularly imprinted solid-phase extractions. *TrAC Trends in Analytical Chemistry* 18(3), 164–174
- Sellergren, B., 1999. Polymer- and template-related factors influencing the efficiency in molecularly imprinted solid-phase extractions. *Trends in Analytical Chemistry* 18, 164–174.
- Sellergren, B., Ekberg, B., Mosbach, K., 1985. Molecular imprinting of amino acid derivatives in macroporous polymers. *Journal of Chromatography* 347, 1–10.
- Shea, K.J., Spivak, D.A., Sellergren, B., 1993. Polymeric complements to nucleotide bases selective binding of adenine derivatives to imprinted polymers. *Journal of the American Chemical Society* 115, 3368-3369
- Spivak, D.A., Gilmore, M.A., Shea, K.J., 1997. Evaluation of Binding and Origins of Specificity of 9-Ethyladenine Imprinted Polymers. *Journal of the American Chemical Society* 119, 4388–4393.
- Svenson, J., Nicholls, I.A., 2001. On the thermal and chemical stability of molecularly imprinted polymers. *Analytica Chimica Acta* 435, 19-24.
- Szabelski, P., Kaczmarek, K., Cavazzini, A., Chen, Y.B., Sellergren, B., Guiochon, G., 2002 Energetic heterogeneity of the surface of a molecularly imprinted polymer studied by high-performance liquid chromatography. *Journal of Chromatography A* 964, 99–111.
- Tamayo, F.G., Turiel, E., Martin-Esteban, A., 2007, Molecularly imprinted polymers for solid-phase extraction and solid-phase microextraction: Recent developments and future trends. *Journal of Chromatography A* 1152, 32-40.
- Urraca, J.L., Hall, A.J., Moreno-Bondi, M.C., Sellergren, B., 2006. A stoichiometric molecularly imprinted polymer for

- the class-selective recognition of antibiotics in aqueous media. *Angewandte Chemie International Edition* 45, 5158–5161.
- Vasapollo, G., Sole, R.D., Mergola, L., Lazzoi, M. R., Scardino, A., Scorrano, S., Mele, G., 2011. Molecularly Imprinted Polymers: Present and Future Prospective, *International Journal of Molecular Science* 12, 5908–5945.
- Vlatakis, G., Andersson, L.L., Muller, R., Mosbach, K., 1993. *Nature*. 361, 645.
- Wei, S., Mizaiikoff, B., 2007. Recent advances on noncovalent molecular imprints for affinity separations. *Journal of Separation Science* 30, 1794–1805.
- Wulff, G., 1995. Molecular imprinting in cross-linked materials with the aid of molecular templates. A way towards artificial antibodies. *Angewandte Chemie International Edition in English* 34, 1812–1832.
- Ye, L., Cormack, P.A.G., Mosbach, K., 1999. Molecularly imprinted monodisperse microspheres for competitive radioassay. *Communications Analytical Communications* 36, 35-38.
- Ye, L., Cormack, P.A.G., Mosbach, K., 2001. Molecular imprinting on microgel spheres. *Analytica Chimica Acta* 435(1), 187–196.
- Ye, L., Weiss, R., Mosbach, K., 2000. Synthesis and characterization of molecularly imprinted microspheres. *Macromolecules* 33, 8239–8245.
- Yoshimatsu, K., Reimhult, K., Krozer, A., Mosbach, K., Sode, K., Ye, L., 2007. Uniform molecularly imprinted microspheres and nanoparticles prepared by precipitation polymerization: The control of particle size suitable for different analytical applications. *Analytica Chimica Acta* 584, 112–121.
- Yu, C., Mosbach, K., 1997. Molecular Imprinting utilizing an aide functional group for hydrogen bonding leading to highly efficient polymers. *The Journal of Organic Chemistry* 62, 4057-4064
- Zhang, Z-H., Yu-Mei, L., Liu, Y-J, Yao, S-Z., 2003. Microspheres Sensor Based on Molecularly Imprinted Polymer Synthesized by Precipitation polymerization, *Chinese Journal of Chemistry* 22, 550-555.
- Zhao, P., Hao, J., 2013. Tert butylhydroquinone recognition of molecular imprinting electrochemical sensor based on core-shell nanoparticles. *Food Chemistry* 139, 1001–1007

Visit us at: <http://bosajournals.com/chemint/>

Submissions are accepted at: editorci@bosajournals.com OR

bosajournals@gmail.com