



Removal of Pb(II), Zn(II), Cu(II) and Cd(II) from aqueous solutions by adsorption onto olive branches activated carbon: Equilibrium and thermodynamic studies

Abdulfattah Mohammed Alkheraz¹, Aisha Khalifa Ali¹, and Khaled Muftah Elsherif^{2,*}

¹Chemistry Department, Faculty of Science, Misurata University, Misurata, Libya

²Chemistry Department, Faculty of Science, University of Benghazi, Benghazi, Libya

*Corresponding author's E. mail: elsherif27@yahoo.com

ARTICLE INFO

Article type:

Research article

Article history:

Received November 2018

Accepted February 2019

January 2020 Issue

Keywords:

Olive branch

Heavy metals

Biosorption

Equilibrium

Thermodynamics

ABSTRACT

The equilibrium and thermodynamics of the biosorption of Pb(II), Zn(II), Cu(II), and Cd(II) onto activated carbon prepared from olive branches were studied under different parameters of pH, initial concentration, and temperature. The batch biosorption procedure was used to find the optimum conditions. The biosorption of each metal ion was found to be pH-dependent. The maximum metal ion biosorption was achieved at pH value 5 for Pb, Cu, and Cd ions and at pH 3 for Zn ions. The extent of the metal ion biosorption increased with temperature (indicating the endothermic character) and initial metal ion concentration. The experimental data of metal ion biosorption were analyzed by Freundlich and Langmuir isotherm models. For all metal ions, the Freundlich isotherm model gave a better fit with higher correlation (R^2) to equilibrium data than Langmuir model. The adsorption capacity values were 41.32, 34.97, 43.10, and 38.17 (mg/g) for Pb(II), Zn(II), Cu(II) and Cd(II), respectively. Thermodynamically parameters, like Gibbs free energy (ΔG°), enthalpy (ΔH°), and entropy (ΔS°) were calculated. The biosorption of each metal ion was non-spontaneous and the order of non-spontaneity of the biosorption process being Zn(II) > Cu(II) > Cd(II) > Pb(II). Likewise, change in entropy was noticed for each metal ion and the order of disorder was Pb(II) > Cd(II) > Cu(II) > Zn(II).

© 2020 International Scientific Organization: All rights reserved.

Capsule Summary: Activated carbon prepared from olive branches is considered to be a low-cost, high efficient, environmental friendly biosorbent and have removed more than 90% metal ions under optimized conditions.

Cite This Article As: A. M. Alkheraz, A. K. Ali, and K. M. Elsherif. Removal of Pb(II), Zn(II), Cu(II) and Cd(II) from aqueous solutions by adsorption onto olive branches activated carbon: Equilibrium and thermodynamic studies. Chemistry International 6(1) (2020) 11-20. <https://doi.org/10.5281/zenodo.2579465>

INTRODUCTION

Recently, due to fast industrialization, environmental contamination is being noticed around the world. The rate of waste and synthetic chemicals disposed into the aquatic environment is raised day by day (Alqadami et al., 2017). Contaminations by heavy metals have remarkably extended

due to industrial flux of smelting, battery manufacturing, mining, tanneries, metallurgical, municipal waste generation, pesticide and fertilizers applications (da Silva et al. 2016; Han, 2016; Pugazhendhi et al. 2018). In the globe, heavy metals are utilized in various industrial sectors due to which metals which are extremely toxic pollutant to the environment are released as waste (Bhateria and Dhaka, 2017). The prevalent heavy metal contaminants specifically,

lead, cadmium, copper, arsenic, mercury, nickel, etc., are non-biodegradable, considerably toxic to humans and also leads to ecological imbalances (Benvenuti et al. 2017; Cardoso et al. 2017). These metals can reach the human body and results in brain and bone damage, nervous system damage, neurological disorders and even cancer (Rao and Khatoun, 2017). Various methods are used to remove heavy metals from industrial waste water, such as: solvent extraction, biological treatment, ionic exchange, adsorption on activated carbon, reverse osmosis, electrolytic methods and membrane filtration (Dursun et al. 2005; Elsherif et al., 2013a; 2013b; 2014a; 2014b; 2014c; Elsherif and Yaghi, 2016; 2017a; 2017b). Among these methods, the adsorption method is the simplest, cheapest, and fastest one for heavy metals removal and also applicable for lower concentration levels (Rodrigues et al., 2013; do Nascimento et al., 2019; Jaafari and Yaghmaeian, 2019; Londono-Zuluaga et al., 2019; Massoud et al., 2019; Moreira et al., 2019; Peng et al., 2019; Yin et al., 2019). Activated carbon is considered to be an effective method for heavy metals removal from polluted waste waters due to its higher surface area, microporosity, and high adsorption capacity (Hameed, 2008; Rodrigues et al. 2011). Activated carbon obtained from biosorbents has the desired surface area and pore volume and accordingly, it has emerged as a potential alternative for activated carbon production (de Sousa Ribeiro et al., 2017).

In our previous work, we used olive leaves, coffee, tea, and orange peels powders as biosorbents for removing heavy metals from aqueous solutions (Elsherif et al., 2017a; 2017b; 2018a; 2018b; 2019). In the present study, factors affecting the biosorption efficiency of Pb(II), Cd(II), Zn(II), and Cu(II) onto activated carbon prepared from olive branches have been studied. Equilibrium studies using various models have been also investigated. Also, thermodynamic parameters of the system have also been determined.

MATERIAL AND METHODS

Chemical and reagents

Lead(II) Nitrate, ACS Reagent, ≥99%, from Honeywell Fluka, Zinc(II) Nitrate Hexahydrate, 98%, Reagent grade, from Honeywell, Copper(II) Nitrate Hemi(Pentahydrate), 98.0 to 102.0%, ACS Reagent, from Honeywell Fluka, Cadmium(II) nitrate tetrahydrate, 98%, ACS Reagent, from Merck, were used to prepare 1000 mg/L stock solutions of metal ions and using double distilled water. Desired test solutions of metal ions were prepared using appropriate subsequent dilutions of the stock solution. The range of concentrations of metal ions prepared from standard solution varies between 50 and 750 mg/L. Before mixing the adsorbent, the pH of each test solution was adjusted to the required value with 0.1 M NaOH or 0.1 M HCl. Sodium hydroxide, BioXtra, ≥98% (acidimetric), pellets (anhydrous), from Merck and hydrochloric acid, ACS reagent, 37%, from Merck were used to prepare these solutions.

Preparation of activated carbon

Olive branches were collected from Misurata city in Libya. It was cleaned, dried, ground, activated with H₃PO₄, and then carbonized using the procedure reported by Isah et al. (Isah et al, 2015). The product was washed and filtered several times with distilled water and then subsequently dried in an oven at 70°C for 24 h.

Analysis

The concentrations of Pb (II), Cd (II), Zn (II), and Cu (II) ions in the solutions before and after equilibrium were determined by atomic absorption machine Shimadzu AA7000. The pH of the solution was measured with pH Meter 3505 from JENWAY.

Biosorption experiments

Batch biosorption experiments were conducted by mixing biosorbent with metal ion solutions with desired concentration in 250 mL conical flasks. The conical flasks were stoppered during the equilibration period and placed on a temperature controlled shaker at a speed 150 r/min. The amount of biosorption was calculated based (Eq. 1) on the difference between the initial (C₀, mg/L) and final concentration (C_e, mg/L).

$$Q_e = \frac{C_0 - C_e}{M} \cdot V \quad (1)$$

Where, Q_e is the metal uptake capacity (mg/g), C₀ is the initial concentration, C_e is the final concentration, V the volume of the metal solution in the conical flask (L) and M is the dry mass of biosorbent (g). The biosorption efficiency % E was calculated as shown in Eq. 2.

$$\% R = \frac{C_0 - C_e}{C_0} \cdot 100 \quad (2)$$

Effect of concentration

The influence of initial metal ion concentration ranging from 50 to 1000 ppm was investigated by contacting a fixed biosorbent mass 1.0 g with 50 mL of aqueous solutions at 303 K for 24 hours.

Effect of pH

Metal ion solutions (50 ml) were taken in four separate conical flasks. The pH of solutions was maintained at pH 2, pH 3, pH 5, pH 7, and pH 10. Olive branches activated carbon 1.0 g was added to each flask and the solutions were stirred for 24 hours at 303 K. After the adsorption test each solution was filtered and the metal ion concentration was checked by AAS.

Effect of biosorbent particle size

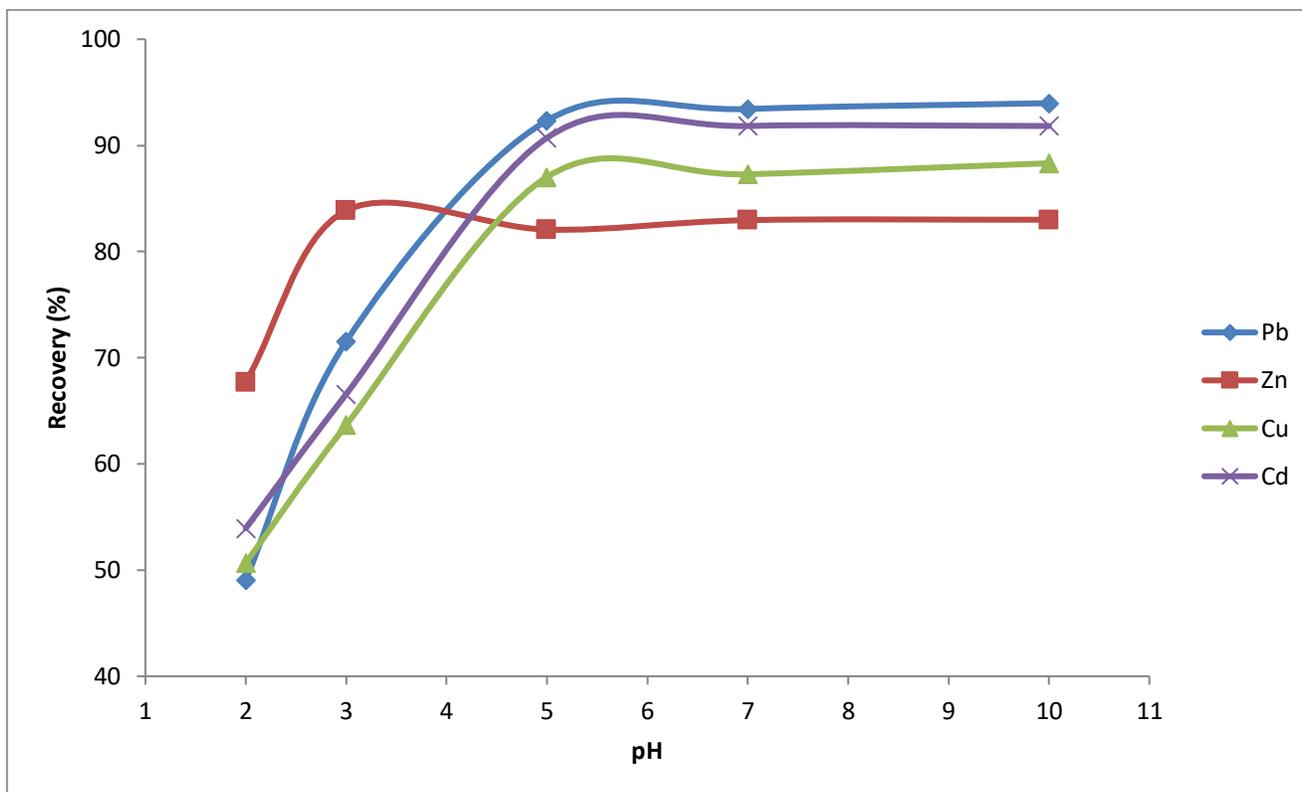


Fig. 1: Effect of pH on Pb, Zn, Cu and Cd biosorption

Adsorption experiments with activated carbon prepared from Olive branches of different particle size were studied. For that purpose, the particle size of 125, 500, 800 μm have been used. Also, three concentrations, 1000, 500, 250 ppm, of the elements were tested with each particle size. The adsorbent dose and solution volume were 1.0 g and 50 ml, respectively.

Effect of temperature

The effect of temperature on the adsorption of Pb, Zn, Cu, and Cd was studied by contacting 1.0 g of adsorbent with 50 mL of metal solution of 100 ppm initial concentration at different temperatures (303, 313, and 323 K).

RESULTS AND DISCUSSION

Effect of pH

The influence of hydrogen ion concentration is one of the most important parameter which has to be investigated in the removal of heavy metals. pH affects the solubility of metal ions and also the functionalization of the microbial adsorbent surface. Figure 1 displays that at extremely acidic solutions ($\text{pH} < 2.0$), the removal of metal ions was minimal. As the pH value was raised from 2.0 to 5.0, there was an increase in metal ion uptake and the maximum

removal of Pb, Cu, and Cd was achieved at pH 5.0 and for Zn at pH of 3.0. When pH was further increased, the metal ions uptake remained mostly unchanged. However, the speciation of the metal ions is considerably altered with change in pH which in turn impacts the removal capacity. From the results, it is shown that biosorption of metal ions is pH dependent and affects the removal capacity of the biosorbent. At lower pH values, functional groups such as carboxylate on biosorbent wall will be protonated and the surface will be positively charged and consequently the H^+ ions will compete with metal ions, thereby leading to minimal biosorption of metal ions. This low biosorption is also due to the repulsion between positively charged H^+ ions and metal ions. As the pH raises, repulsions between the H^+ ions and metal ions decreases which leads to more metal uptake at the biosorption site. And also, as pH raises, the number of negatively charged sites increases resulting in gradual increase in the biosorption of metal ions.

Effect of biosorbent particle size

The effect of particle size as presented in Figure 2 showed that the metal ions uptake decreased as the particle size increases. The effect of particle size of activated carbon prepared from Olive branches was examined for three metal ion concentrations which were 1000, 500, and 250 ppm.

Table 1: Langmuir and Freundlich isotherms parameters

Ion metal	Pb	Zn	Cu	Cd
		Freundlich		
R ²	0.992	0.993	0.985	0.998
K _F	1.31	1.23	1.15	1.39
n	1.70	1.73	1.53	1.85
		Langmuir		
R ²	0.979	0.926	0.995	0.945
K _L (L/mg)	0.013	0.007	0.009	0.012
Q _m (mg/g)	41.32	34.97	43.10	38.17

Table 2: Thermodynamic parameters for the biosorption of metal ions onto Olive branches activated carbon

Metal ion	T, K	ΔG°, kJ/mol	ΔH°, kJ/mol	ΔS°, J/mol.K	R ²
Pb	303	1.29	16.25	49.36	0.995
	313	0.80			
	323	0.31			
Zn	303	3.37	9.38	19.84	0.871
	313	3.17			
	323	2.97			
Cu	303	2.9	9.43	21.56	0.954
	313	2.68			
	323	2.47			
Cd	303	1.85	12.85	36.31	0.967
	313	1.48			
	323	1.12			

Effect of metal ion concentration (Biosorption Isotherms)

The influence of initial metal concentration on biosorption is ordinarily investigated to find out the dependent of the initial metal ions concentration in aqueous phase and the metal biosorption capacity of biosorbent. The uptake of metal ions is dependent on initial concentration and it increases with increasing in initial concentration as shown in Figure 3. This change in biosorption at different concentrations of metal ions is due to the enhancement in the motivating gradient force. At higher concentrations, there were a greater driving force to transport the metals. But at extremely high concentration of metals, the binding sites will be saturated. It is substantial to find out the maximum biosorption capacity of biosorbent, so as to conduct the experiment at the highest possible initial metal concentration. Hence the initial concentration of metal ions supplies a driving force and also reduces the mass transfer resistance for allowing metal biosorption.

However, the equilibrium data obtained was analyzed using Langmuir and Freundlich adsorption isotherm model equations (Elsherif et al, 2018a; 2018b) and the plots are presented in Figures 4 and 5. The Eqs. 3-4 are expressing the Langmuir and Freundlich isotherms, respectively.

$$\frac{C_e}{Q_e} = \frac{1}{K_L Q_m} + \frac{C_e}{Q_m} \quad (3)$$

$$\text{Log} Q_e = \text{Log} K_F + \frac{1}{n} \text{Log} C_e \quad (4)$$

Where, Q_e represents metal uptake capacity in mg/g, Q_m represents maximum metal uptake capacity in mg/g, C_e represents equilibrium concentration in mg/L; K_L and K_F are the constants related to its intensity and n is a measure of feasibility of the adsorbents. The results obtained from the modeling showed that the removal of Pb, Zn, Cu, and Cd ions using activated carbon prepared from Olive branches followed Freundlich adsorption equation with higher correlation coefficients (R^2) of about 0.99 for all metal ions. The implication of Langmuir correlation revealed that the Cu(II) ion has a maximum adsorption capacity while the Zn(II) ion has the lowest. Generally, the result showed that the interaction between the metal ions and the surface of the Olive branches activated carbon was indicative of a physical type of adsorption. The parameters for these models are presented in Table 1.

Effect of temperature (Thermodynamic parameters)

Temperature is a more significant consideration which affects the biosorption of heavy metals. The biosorption of metal ions onto olive branch activated carbon increased with increase in temperature from 303 to 323 K (Fig. 6).

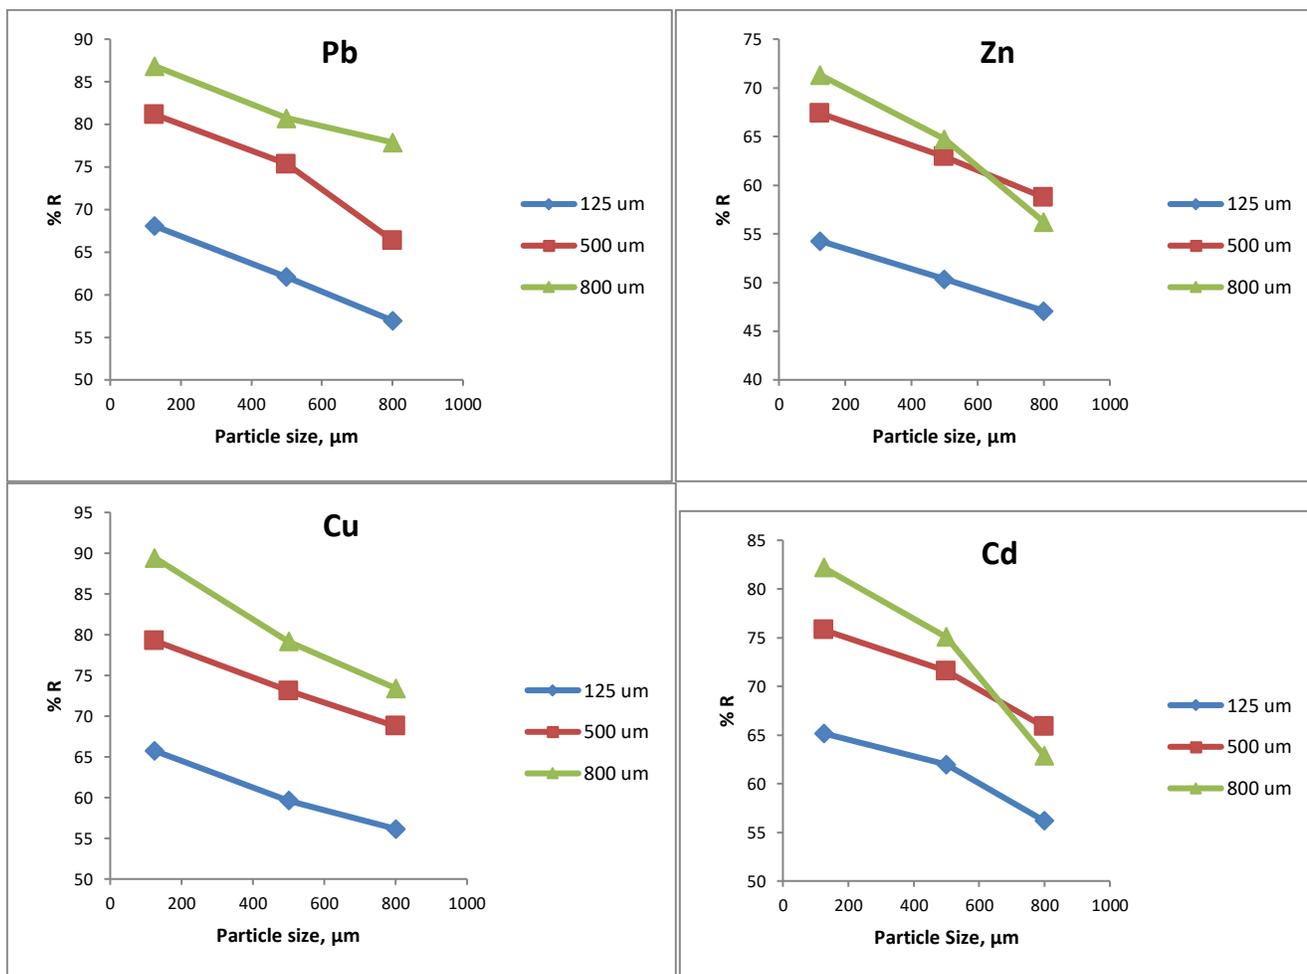


Fig. 2: Effect of particle size on Pb, Zn, Cu, and Cd biosorption (R = recovery)

Increasing in adsorption at higher temperature values is due to the strengthening of the interaction between the metal ion and active sites. Moreover, higher temperatures will also motivate more mobility in the particles and reduces the liquid viscosity. Conventionally, the adsorption process takes place in two accompanying processes, which will be a fast diffusion and slow complexation. The increase in temperature will not only speeds up the diffusion rate of metal ions from solution to the surface of biosorbent, but also accelerates the complexation of metal ions with the functional groups of the biosorbent (Ding et al., 2019; Gupta et al., 2019; Hadiani et al., 2019; Noormohamadi et al., 2019; Que et al., 2019; Rai et al., 2019; Sedlakova-Kadukova et al., 2019; Wu et al., 2019; Xu et al., 2019). In order to describe thermodynamic behavior of the biosorption of metal ions onto olive branches activated carbon, thermodynamic parameters including the change in free energy (ΔG°), enthalpy (ΔH°) and entropy (ΔS°) were calculated using relation shown in Eq. 5 (Farhan et al., 2012).

$$\Delta G^\circ = -RT \ln K_D \quad (5)$$

Where, R is the universal gas constant (8.314J/mol K), T (K) is the temperature and K_D is the distribution coefficient. According to thermodynamics, the Gibb's free energy change is also related to the enthalpy change (ΔH°) and entropy change (ΔS°) at constant temperature by the Van't Hoff equation (Farhan et al., 2012).

$$\Delta G^\circ = \Delta H^\circ - T\Delta S^\circ \quad (6)$$

Equations (5) and (6) can be written as:

$$\ln K_D = -\frac{\Delta H^\circ}{RT} + \frac{\Delta S^\circ}{R} \quad (7)$$

According to the equation 5, the values of enthalpy change (ΔH°) and entropy change (ΔS°) were calculated from the slope and intercept of the plot of $\ln K_D$ vs. $1/T$ (Fig. 7). The calculated values of thermodynamic parameters (ΔG° , ΔH° , and ΔS°) for the biosorption of metal ions onto olive branches activated carbon are reported in Table 2.

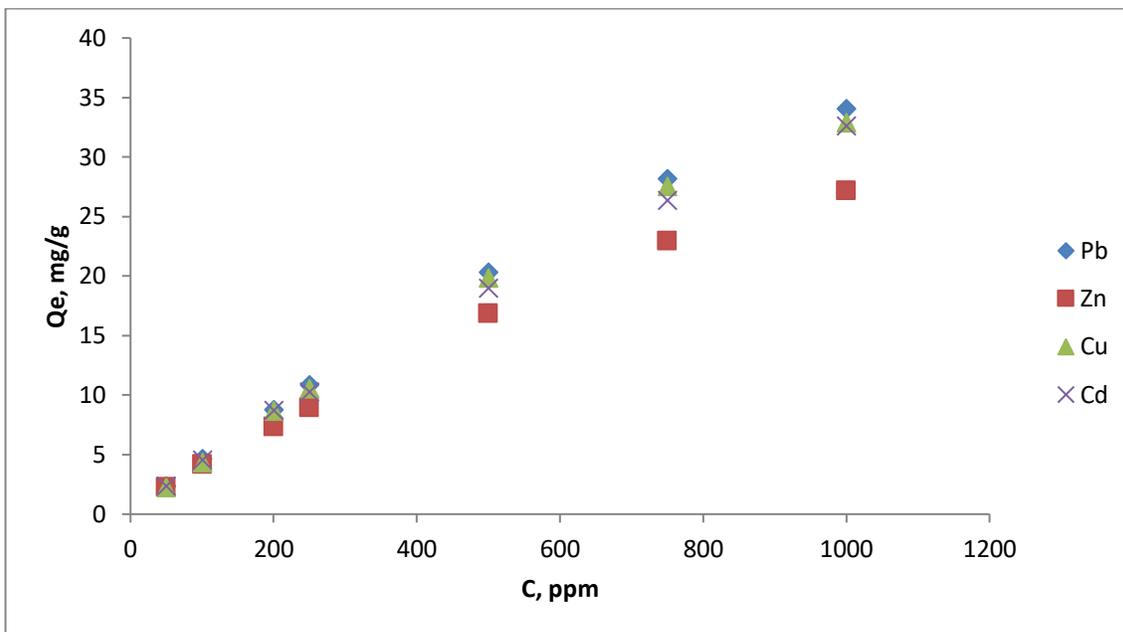


Fig. 3: Effect of initial concentration on metal ion biosorption

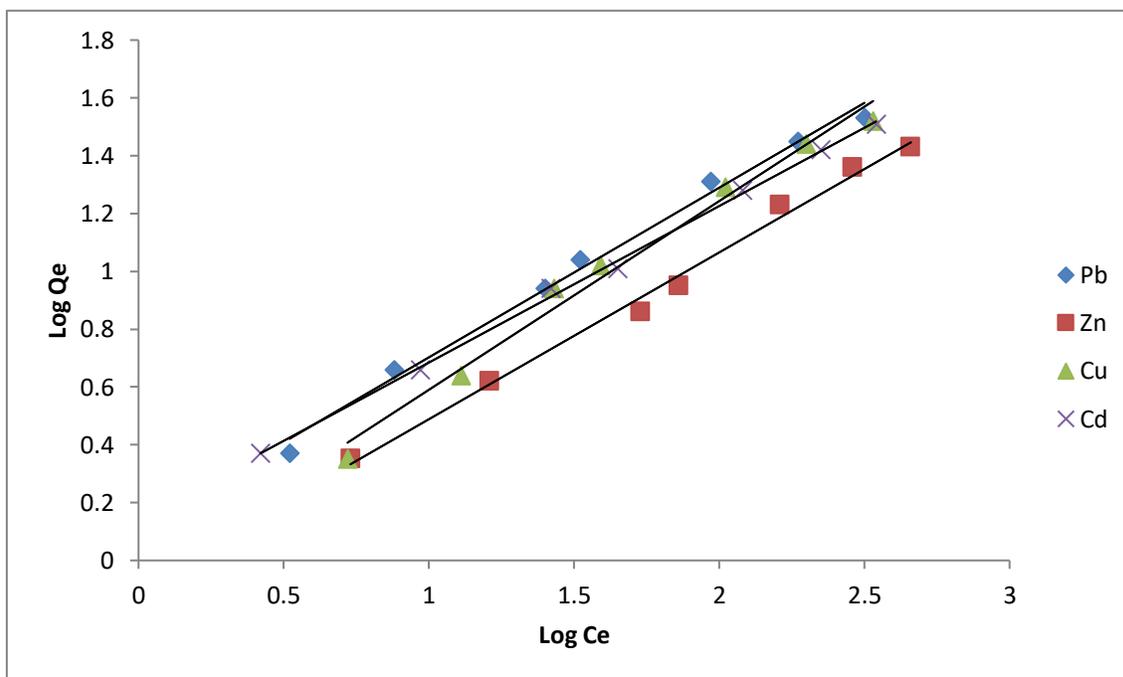


Fig. 4: Equilibrium studies of metal ions biosorption onto Olive branches activated carbon (Freundlich isotherm)

A positive value of the free energy (ΔG°) indicated the non-spontaneous nature of the biosorption process. The physical adsorption the free energy change (ΔG°) ranges from (-20 to 0) kJ/mol and for chemical adsorption it ranges between (-80 and -400) kJ/mol.

The ΔG° (Lohaniet al., 2008), for metal ions adsorption onto olive branches activated carbon was in the

range of (0.80 to 3.37) kJ/mol and so the adsorption was more likely a physical adsorption. A positive value of ΔS° as 19.84-49.36 J/mol.K showed increased randomness at solid solution interface during the adsorption of metal ions (Cataldo et al., 2018; Marciniak et al., 2019; Zhuang et al., 2019).

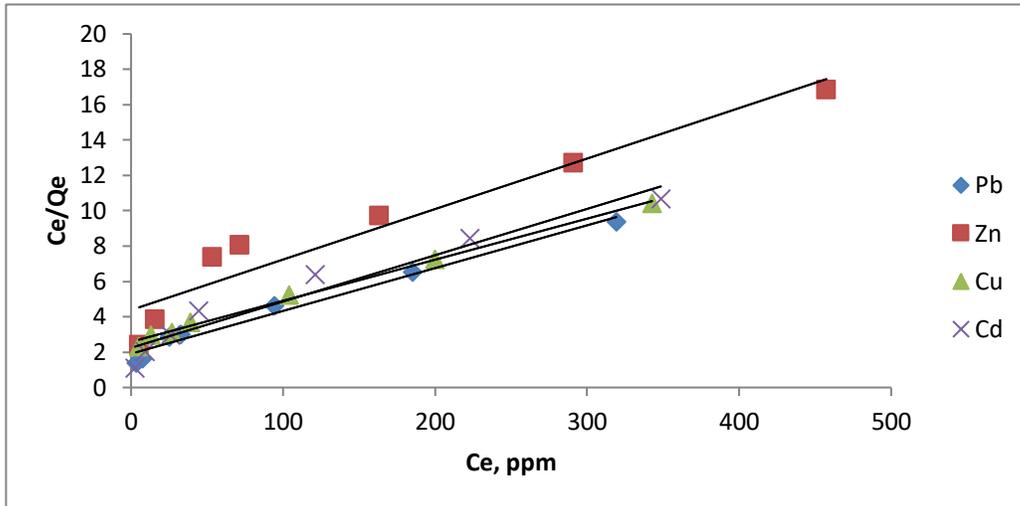


Fig. 5: Equilibrium studies of metal ions biosorption onto Olive branches activated carbon (Langmuir isotherm)

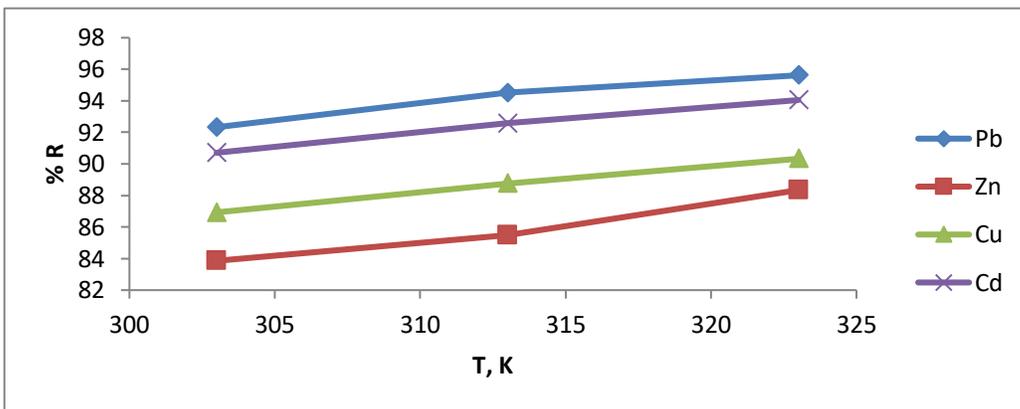


Fig. 6: Effect of temperature on biosorption efficiency of metal ions

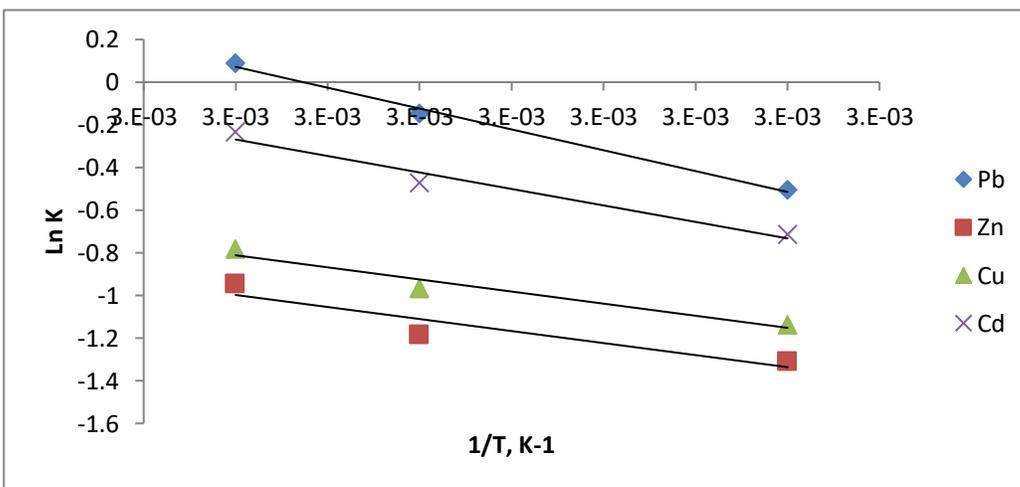


Fig. 7: Plots of In Ka against 1/T for metal ions biosorption

CONCLUSIONS

The biosorption of Pb(II), Zn(II), Cu(II) and Cd(II) by activated carbon prepared from olive branches under several circumstances was investigated. The pH has the most influence on the biosorption of these metal ions from aqueous solutions. The biosorption isotherms of the metal ions onto the olive branches activated carbon are well described by Freundlich isotherm model. The thermodynamic study demonstrated that the biosorption of all metal ions was non-spontaneous. The present study reveals that olive branches activated carbon has high potential for handling industrial waste waters containing heavy metals.

REFERENCES

- Alqadami, A.A., Naushad, M., Abdalla, M.A., Ahamad, T., Abdullah ALOthman, Z., Alshehri, S.M., Ghfar, A.A., 2017. Efficient removal of toxic metal ions from wastewater using a recyclable nanocomposite: A study of adsorption parameters and interaction mechanism. *Journal of Cleaner Production* 156, 426-436.
- Benvenuti, T., Siqueira Rodrigues, M.A., Bernardes, A.M., Zoppas-Ferreira, J., 2017. Closing the loop in the electroplating industry by electrodialysis. *Journal of Cleaner Production* 155, 130-138.
- Bhateria, R., Dhaka, R., 2017. Impact of electroplating effluent on growth of *Triticum aestivum* and *Hordeum vulgare*. *Environmental Technology and Innovation* 8, 389-398.
- Cardoso, S.L., Costa, C.S.D., Nishikawa, E., da Silva, M.G.C., Vieira, M.G.A., 2017. Biosorption of toxic metals using the alginate extraction residue from the brown algae *Sargassum filipendula* as a natural ion-exchanger. *Journal of Cleaner Production* 165, 491-499.
- Cataldo, S., Chiodo, V., Crea, F., Maisano, S., Milea, D., Pettignano, A., 2018. Biochar from byproduct to high value added material – A new adsorbent for toxic metal ions removal from aqueous solutions. *Journal of Molecular Liquids* 271, 481-489.
- da Silva, T.L., da Silva Junior, A.C., Vieira, M.G.A., Gimenes, M.L., da Silva, M.G.C., 2016. Biosorption study of copper and zinc by particles produced from silk sericin e alginate blend: evaluation of blend proportion and thermal crosslinking process in particles production. *Journal of Cleaner Production* 137, 1470-1478.
- de Sousa Ribeiro, L.A., Rodrigues, L.A., Thim, G.P., 2017. Preparation of activated carbon from orange peel and its application for phenol removal. *International Journal of Engineering Science* 3(3), 122-129.
- Ding, H., Luo, X., Zhang, X., Yang, H., 2019. Alginate-immobilized *Aspergillus niger*: Characterization and biosorption removal of thorium ions from radioactive wastewater. *Colloids and Surfaces A: Physicochemical and Engineering Aspects* 562, 186-195.
- do Nascimento, J.M., de Oliveira, J.D., Rizzo, A.C.L., Leite, S.G.F., 2019. Biosorption Cu (II) by the yeast *Saccharomyces cerevisiae*. *Biotechnology Reports* 21, e00315.
- Dursun, G., Çiçek, H., Dursun, A.Y., 2005. Adsorption of phenol from aqueous solution by using carbonised beet pulp. *Journal of Hazardous Materials* 125, 175-182.
- Elsherif, K.M., and Yaghi, M.M., 2017. Membrane potential studies of parchment supported silver oxalate membrane. *Journal of Materials and Environmental Science* 8(1), 356-363.
- Elsherif, K.M., El-Hashani, A., El-Dali, A., 2013. Effect of temperature on membrane potential and evaluation of thermodynamic parameters of parchment supported silver thiosulphate. *Der Chemica Sinica* 4(6), 13-21.
- Elsherif, K.M., El-Hashani, A., El-Dali, A., 2013. Potentiometric determination of fixed charge density and permselectivity for thallium chromate membrane. *Annalen der Chemischen Forschung* 1(3), 15-25.
- Elsherif, K.M., El-Hashani, A., El-Dali, A., El-kailany, R., 2014. Bi-ionic potential studies for silver thiosulphate parchment-supported membrane. *International Journal of Advanced Scientific and technical Research* 1(4), 638-646.
- Elsherif, K.M., El-Hashani, A., El-Dali, A., Musa, M., 2014. Ion selectivity across parchment-supported silver chloride membrane in contact with multi-valent electrolytes. *International Journal of Analytical and Bioanalytical Chemistry* 4(2), 58-62.
- Elsherif, K.M., El-Hashani, A., El-Dali, A., Saad, M., 2014. Ion-permeation rate of (1:1) electrolytes across parchment-supported silver chloride membrane. *International Journal of Chemistry and Pharmaceutical Sciences* 2(6), 885-892.
- Elsherif, K.M., El-Hashani, A., Haider, I., 2018. Equilibrium and kinetic studies of Cu(II) biosorption onto waste tea and coffee powder (WTCP). *Iranian Journal of Analytical Chemistry* 5(2), 31-38.
- Elsherif, K.M., El-Hashani, A., Haider, I., 2018. Biosorption of Fe(III) onto coffee and tea powder: Equilibrium and kinetic study, *Asian Journal of Green Chemistry* 2(4), 380-394.
- Elsherif, K.M., El-Hashani, A., Haider, I., 2019. Biosorption of Co(II) ions from aqueous solution onto coffee and tea powder: Equilibrium and kinetic studies, *Journal of Fundamental and Applied Sciences* 11(1), 65-81.
- Elsherif, K.M., Ewlad-Ahmed, A.M., Treban, A., 2017. Biosorption studies of Fe(III), Cu(II), and Co(II) from aqueous solutions by olive leaves powder. *Applied Journal of Environmental Engineering Science* 3(4), 341-352.
- Elsherif, K.M., Ewlad-Ahmed, A.M., Treban, A., 2017. Removal Of Fe (III), Cu (II), And Co(II) from aqueous solutions by orange peels powder: Equilibrium study, *Journal of Biochemistry and Molecular Biology Research* 2(6), 46-51.
- Elsherif, K.M., Yaghi, M.M., 2017. Studies with model membrane: Determination of fixed charge density of

- silver sulfite membrane, American Journal of Polymer Science and Technology 2(2), 28-33.
- Elsherif, K.M., Yaghi, M.M., 2017. Studies With Model Membrane: The Effect Of Temperature On Membrane Potential. Moroccan Journal of Chemistry 5(1), 131-138.
- Farhan, A.M., Salem, N.M., Ahmad, A.L., Awwad, A.M., 2012. Kinetic, equilibrium and thermodynamic studies of the biosorption of heavy metals by *Ceratonia siliqua* Bark, American Journal of Analytical Chemistry 2(6), 335-342.
- Gupta, N.K., Gupta, A., Ramteke, P., Sahoo, H., Sengupta, A., 2019. Biosorption-a green method for the preconcentration of rare earth elements (REEs) from waste solutions: A review. Journal of Molecular Liquids 274, 148-164.
- Hadiani, M.R., Khosravi-Darani, K., Rahimifard, N., 2019. Optimization of As(III) and As(V) removal by *Saccharomyces cerevisiae* biomass for biosorption of critical levels in the food and water resources. Journal of Environmental Chemical Engineering 7, 102949.
- Hameed, B.H., Rahman, A., 2008. Removal of phenol from aqueous solutions by adsorption onto activated carbon prepared from biomass material, Journal of Hazardous Materials 160, 576-581.
- Han, W., Fu, F., Cheng, Z., Tang, B., Wu, S., 2016. Studies on the optimum conditions using acid-washed zero-valent iron/aluminum mixtures in permeable reactive barriers for the removal of different heavy metal ions from wastewater. Journal of Hazardous Materials 302, 437-446.
- Isah, A.U., Abdulraheem, G., Bala, S., Muhammad, S., Abdullahi, M., 2015. Kinetics, equilibrium and thermodynamics studies of C.I. Reactive Blue 19 dye adsorption on coconut shell based activated carbon. International Biodeterioration and Biodegradation 102, 265-273.
- Jaafari, J., Yaghmaeian, K., 2019. Optimization of heavy metal biosorption onto freshwater algae (*Chlorella coloniales*) using response surface methodology (RSM). Chemosphere 217, 447-455.
- Khan Rao, R.A., Khatoun, A., 2017. Aluminate treated *Casuarina equisetifolia* leaves as potential adsorbent for sequestering Cu(II), Pb(II) and Ni(II) from aqueous solution. Journal of Cleaner Production 165, 1280-1295.
- Lohani, M.B., Singh, A., Rupainwar, D.C., Dhar, D.N., 2008. Studies on efficiency of guava (*Psidium guajava*) bark as biosorbent for removal of Hg(II) from aqueous solutions. Journal of Hazardous Materials 159, 626-629.
- Londono-Zuluaga, C., Jameel, H., Gonzalez, R.W., Lucia, L., 2019. Crustacean shell-based biosorption water remediation platforms: Status and perspectives. Journal of Environmental Management 231, 757-762.
- Marciniak, M., Goscianska, J., Frankowski, M., Pietrzak, R., 2019. Optimal synthesis of oxidized mesoporous carbons for the adsorption of heavy metal ions. Journal of Molecular Liquids 276, 630-637.
- Massoud, R., Hadiani, M.R., Hamzehlou, P., Khosravi-Darani, K., 2019. Bioremediation of heavy metals in food industry: Application of *Saccharomyces cerevisiae*. Electronic Journal of Biotechnology 37, 56-60.
- Moreira, V.R., Lebron, Y.A.R., Freire, S.J., Santos, L.V.S., Palladino, F., Jacob, R.S., 2019. Biosorption of copper ions from aqueous solution using *Chlorella pyrenoidosa*: Optimization, equilibrium and kinetics studies. Microchemical Journal 145, 119-129.
- Noormohamadi, H.R., Fat'hi, M.R., Ghaedi, M., Ghezelbash, G.R., 2019. Potentiality of white-rot fungi in biosorption of nickel and cadmium: Modeling optimization and kinetics study. Chemosphere 216, 124-130.
- Peng, H., Li, D., Ye, J., Xu, H., Xie, W., Zhang, Y., Wu, M., Xu, L., Liang, Y., Liu, W., 2019. Biosorption behavior of the *Ochrobactrum* MT180101 on ionic copper and chelate copper. Journal of Environmental Management 235, 224-230.
- Pugazhendhi, A., Boovaragamoorthy, G.M., Ranganathan, K., Naushad, M., Kaliannan, T., 2018. New insight into effective biosorption of lead from aqueous solution using *Ralstonia solanacearum*: Characterization and mechanism studies. Journal of Cleaner Production 174, 1234-1239.
- Que, W., Zhou, Y.-H., Liu, Y.-G., Wen, J., Tan, X.-F., Liu, S.-J., Jiang, L.-h., 2019. Appraising the effect of in-situ remediation of heavy metal contaminated sediment by biochar and activated carbon on Cu immobilization and microbial community. Ecological Engineering 127, 519-526.
- Rai, P.K., Lee, S.S., Zhang, M., Tsang, Y.F., Kim, K.-H., 2019. Heavy metals in food crops: Health risks, fate, mechanisms, and management. Environment International 125, 365-385.
- Rodrigues, L.A., da Silva, M.L.C.P., Alvarez-Mendes, M.O., Coutinho, A.R., Thim, G.P., 2011. Phenol removal from aqueous solution by activated carbon produced from avocado kernel seeds. Chemical Engineering Journal 174, 49-57.
- Rodrigues, L.A., Sousa Ribeiro, L.A., Thim, G.P., Ferreira, R.R., Alvarez-Mendez, M.O., Coutinho, A.D.R., 2012. Activated carbon derived from macadamia nut shells: an effective adsorbent for phenol removal. Journal of Porous Materials 20, 619.
- Sedlakova-Kadukova, J., Kopcakova, A., Gresakova, L., Godany, A., Pristas, P., 2019. Bioaccumulation and biosorption of zinc by a novel *Streptomyces* K11 strain isolated from highly alkaline aluminium brown mud disposal site. Ecotoxicology and Environmental Safety 167, 204-211.
- Wu, Y., Qiu, X., Cao, S., Chen, J., Shi, X., Du, Y., Deng, H., 2019. Adsorption of natural composite sandwich-like nanofibrous mats for heavy metals in aquatic environment. Journal of Colloid and Interface Science 539, 533-544.
- Xu, Y., Seshadri, B., Bolan, N., Sarkar, B., Ok, Y.S., Zhang, W., Rumpel, C., Sparks, D., Farrell, M., Hall, T., Dong, Z., 2019. Microbial functional diversity and carbon use feedback in soils as affected by heavy metals. Environment International 125, 478-488.

Yin, K., Wang, Q., Lv, M., Chen, L., 2019. Microorganism remediation strategies towards heavy metals. Chemical Engineering Journal 360, 1553-1563.

Zhuang, S., Cheng, R., Wang, J., 2019. Adsorption of diclofenac from aqueous solution using UiO-66-type metal-organic frameworks. Chemical Engineering Journal 359, 354-362.

Visit us at: <http://bosaljournals.com/chemint/>
Submissions are accepted at: editorci@bosaljournals.com